

Composite CaWO_4 Detectors for the CRESST-II Experiment

M. Kiefer^{*}, G. Angloher^{*}, M. Bauer[†], I. Bavykina^{*}, A. Bento^{*,**}, A. Brown[‡],
 C. Bucci[§], C. Ciemniak[¶], C. Coppi[¶], G. Deuter[†], F. von Feilitzsch[¶], D. Hauff^{*},
 S. Henry[‡], P. Huff^{*}, J. Imber[‡], S. Ingleby[‡], C. Isaila[¶], J. Jochum[†], M. Kimmerle[†],
 H. Kraus[‡], J.-C. Lanfranchi[¶], R. F. Lang^{*}, M. Malek[‡], R. McGowan[‡],
 V. B. Mikhailik[‡], E. Pantic^{*}, F. Petricca^{*}, S. Pfister[¶], W. Potzel[¶], F. Pröbst^{*}, S. Roth[¶],
 K. Rottler[†], C. Sailer[†], K. Schäffner^{*}, J. Schmalzer^{*}, S. Scholl[†], W. Seidel^{*},
 L. Stodolsky^{*}, A. J. B. Tolhurst[‡], I. Usherov[†] and W. Westphal^{¶,||}

^{*}Max-Planck-Institut für Physik, Föhringer Ring 6, D-80805 München, Germany

[†]Eberhard-Karls-Universität Tübingen, D-72076 Tübingen, Germany

^{**}on leave from: Departamento de Física, Universidade de Coimbra, P3004 516 Coimbra, Portugal

[‡]Department of Physics, University of Oxford, Oxford OX1 3RH, United Kingdom

[§]INFN, Laboratori Nazionali del Gran Sasso, I-67010 Assergi, Italy

[¶]Physik-Department E15, Technische Universität München, D-85747 Garching, Germany

^{||}Deceased

Abstract. CRESST-II, standing for Cryogenic Rare Events Search with Superconducting Thermometers phase II, is an experiment searching for Dark Matter. In the LNGS facility in Gran Sasso, Italy, a cryogenic detector setup is operated in order to detect WIMPs by elastic scattering off nuclei, generating phononic lattice excitations and scintillation light. The thermometers used in the experiment consist of a tungsten thin-film structure evaporated onto the CaWO_4 absorber crystal. The process of evaporation causes a decrease in the scintillation light output. This, together with the need of a big-scale detector production for the upcoming EURECA experiment lead to investigations for producing thermometers on smaller crystals which are glued onto the absorber crystal. In our Run 31 we tested composite detectors for the first time in the Gran Sasso setup. They seem to produce higher light yields as hoped and could provide an additional time based discrimination mechanism for low light yield clamp events.

Keywords: Dark Matter, WIMP, Low temperature detectors, Scintillation detectors, CaWO_4 , Epoxy, Glue

PACS: 95.35.+d, 29.40.Wk, 07.20.Mc, 29.40.Mc

INTRODUCTION

The CRESST-II experiment aims for direct detection of WIMPs via elastic scattering off nuclei of scintillating crystals. The scattering energy of impinging particles is transformed into phonons and scintillation light. The phonons enable us to precisely measure the energy of the particles, while the amount of emitted light enables us to determine their nature [1].

A CRESST-II detector module consists of a phonon detector and a separate light detector [2]. The phonon detector is a cylindrical crystal of scintillating material, while the light detector is a thin wafer optimized for the detection of the scintillation light. The housing around them is covered with scintillating reflector foil. For signal read-out, both crystal and wafer have an evaporated thin film superconducting phase transition thermometer. The high temperature needed for growing good tungsten films results in a degradation of the light output of the scintillator crystal (see Fig.1).

In our previous run [2], we observed 3 events in the

WIMP signal acceptance region. An increase of the detected light signal would answer this question: It should help to clarify whether these events are just neutrons misidentified due to a low light output. Our approach was to increase the light output by avoiding the high temperature treatment of the crystals in vacuum and by this mean to prevent the crystals from degrading.

The concept of composite detectors has been previously explored, for example for GNO [3]. For CRESST, we evaporated tungsten phonon detector thermometers onto small crystals and glued these thermometer carriers onto scintillator crystals of the same material; an example can be seen in Fig. 2. We used two different glues; more details are described in [4]. Run 31 of the CRESST-II experiment included 13 modules with thermometers directly evaporated and four modules with composite detectors. Three of these were CaWO_4 and a fourth one ZnWO_4 [5]. Concerning future plans, the gluing technique might facilitate the detector mass production required for a ton-scale experiment like EURECA [6].

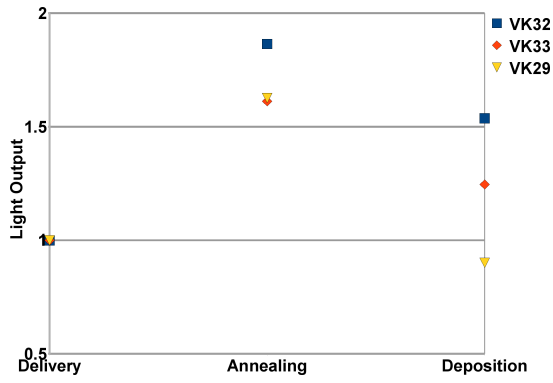


Figure 1. Development of light output of three different crystals during detector production. The values are normalized to the light output at delivery time.

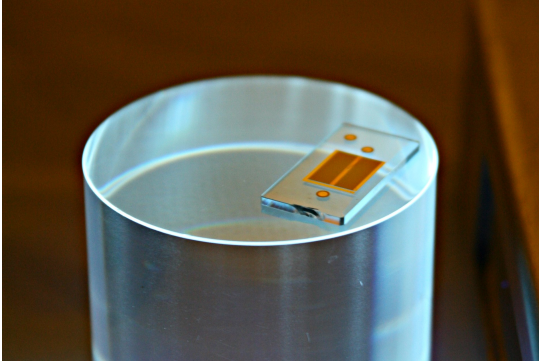


Figure 2. One of the composite phonon detectors, scintillating in UV light.

Results obtained with composite detectors in Run 31 are promising. The pulses of the individual crystals of a composite detector, namely the thermometer carrier and the absorber crystal, can be distinguished by their pulse shape.

EXPERIMENTAL RESULTS

Setup

The scintillating crystals used in CRESST-II have a cylindrical shape of 40 mm height and 40 mm diameter. The thermometer carriers have dimensions of $20 \times 10 \times 1 \text{ mm}^3$. We used two different glues to connect the parts, Araldite 2011 for one detector named Hanna and EpoTek 301-2 for the other two called Maja and Rita. Both types of glue have proven to work under cryogenic conditions before. Nonetheless, after finishing Run 31, the absorber crystal of the detector Hanna was found to be destroyed by a crack reaching from the glue spot through the crys-

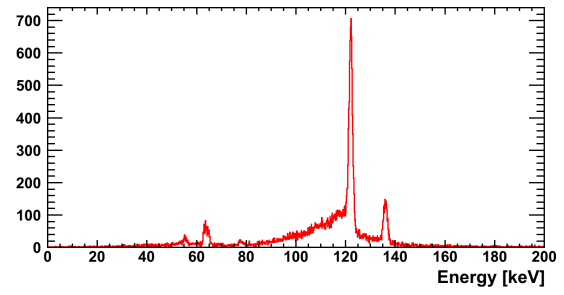


Figure 3. ^{57}Co Calibration spectrum of the phonon detector Maja.

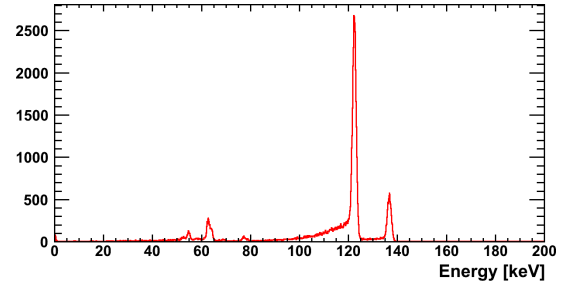


Figure 4. ^{57}Co Calibration spectrum of the phonon detector Julia.

tal. In spite of this fact, the energy resolution in Hanna was sufficient for dark matter search. Unfortunately, due to technical problems the light detector was not functioning so that Rita/Steven was the only composite CaWO_4 module with a working light detector

Calibration spectra

We calibrate detectors by exposing them to γ radiation from a ^{57}Co source. The calibration spectrum recorded with Maja can be seen in Fig. 3. In addition to the lines at 122 and 136 keV, the escape peaks of W and a Pb line can be seen as well. For comparison, Fig. 4 shows the calibration spectrum of Julia, a typical standard phonon detector, that we will use as a reference here. Using the FWHM of the 122 keV line as a reference, one can compare the signal quality of the phonon detectors. Tab. 1 shows the values for the three composite detectors as well as for Julia. The composite detectors perform nearly as good as Julia, with the exception of Hanna, the broken detector.

Light Yield

In order to find out about the nature of a particle event, the data of the light detector and the phonon detector

Table 1. Comparison of the FWHMs of the 122 keV calibration line. Julia is a standard phonon detector while the others are composite detectors.

Name	FWHM [keV]		Comment
	122 keV-Peak	Baseline	
Julia	1.92	0.99	standard
Maja	1.98	0.80	EpoTek
Rita	1.98	0.41	EpoTek
Hanna	2.62	0.44	Araldite, broken

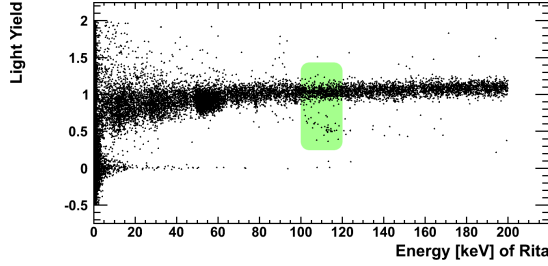


Figure 5. Light yield plot taken with the module Rita/Steven. The shaded area indicates pulses in the energy range of Pb-recoils. For a possible explanation of the events around zero light yield see [7].

have to be combined. This results in a plot where the particle energy, recorded in the phonon detector, is shown on the abscissa. The pulse height of the light signal divided by the particle energy is shown on the ordinate. This so-called Light Yield is normalized to 1 for γ particles at 122 keV. Fig. 5 shows such a plot, taken with the phonon detector Rita and its corresponding light detector Steven. In the shaded region between 100 and 120 keV, there is a population of particle events below the γ band. These events originate from ^{210}Po α -decays where the α -particle is absorbed in the surrounding scintillating reflector foil and the recoiling nucleon hits the CaWO_4 crystal [8]. The light signals show a faster rise time consistent with the fast scintillation time of the plastic reflector foil (see Fig. 6). As the same foil is used in every de-

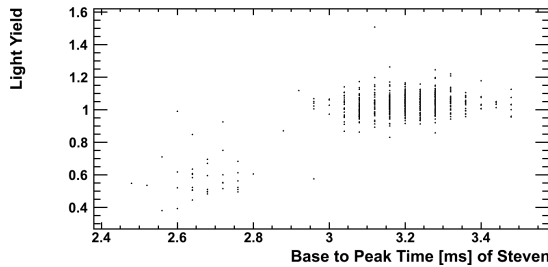


Figure 6. Time from pulse onset to peak vs. Light Yield of the light pulses around 100 keV in Rita/Steven. The different times indicate a fast scintillator as the origin of the events with the lower light yield.

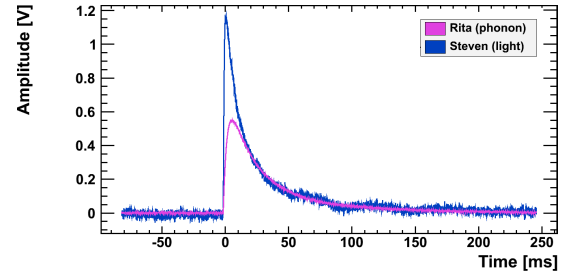


Figure 7. γ event taken with the module Rita/Steven. The energy was absorbed in the absorber crystal.

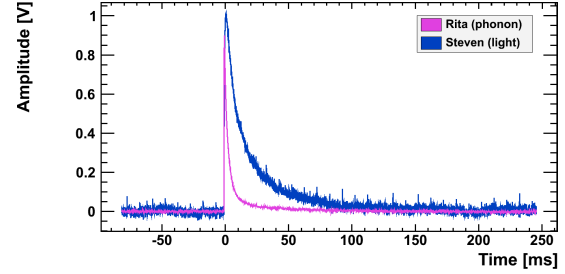


Figure 8. γ event taken with the module Rita/Steven. The energy was absorbed in the thermometer carrier crystal.

tector module, its absolute light yield is the same for every module. Hence it is possible to use the relation of the Light Yield of the γ band and of this spot as a mean for comparing the light output of different scintillator crystals without having installed a dedicated light detector calibration source in each module. By using this method however, there was no significant difference between the detectors Rita and Julia. Analysis of data gathered in Run 32, where the energy scale of the detector was calibrated by shining 6 keV X-rays onto the light detector, resulted in a light output of 2.36 % for Rita which is an extraordinarily high value, compared to standard detectors, where the value is around 1.3 %. The reason for this discrepancy remains to be clarified.

Pulse shapes

Fig. 7 shows a γ event recorded by the module Rita/Steven. The pulse can be described as a sum of three exponentials [9]. When comparing this pulse with the one shown in Fig. 8, one sees that the rise and decay times of the latter are much shorter. The first pulse was caused by an energy deposition in the absorber crystal while in the case of the second pulse, the deposition occurred directly in the thermometer carrier (cf. [4, 10]).

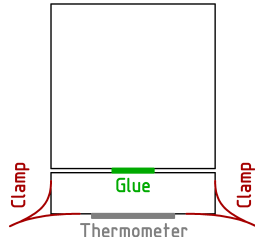


Figure 9. Schematic concept of the clamp-event discrimination detector

FURTHER RESEARCH

In spring of 2009, CRESST started a new run. Run 32 features 13 standard CaWO_4 detectors, two composite CaWO_4 and two composite ZnWO_4 detectors. Additionally, there is a detector which is designed to discriminate events caused by the holding clamps from the events created in the absorber crystal. We have used EpoTek for all composite detectors.

This detector consists of a thermometer film on a CaWO_4 disk of 40 mm diameter and 10 mm height which is glued to a cylindrical absorber crystal of $40\text{ mm} \times 40\text{ mm}$ (see Fig. 9). In contrast to a standard phonon detector, this one is only held by clamps at the smaller disk. The clamp-event discrimination detector takes advantage of the different pulse shapes in order to separate events occurring in the clamps [7] from events occurring in the absorber: The events coming from the clamps should have a pulse shape similar to the events originating from the small part and thus should be distinguishable from events originating in the big absorber crystal.

CONCLUSION

The composite detectors included in Run 31 have generated valuable data. Measurements indicate that the composite detectors might have an advantage in light output, compared to conventional detectors. There is a possibility to use other, more delicate materials such as ZnWO_4 now, that they can be equipped with thermometers which was not possible before. Additionally, the different-sized crystals create pulses with different shapes, providing information about the origin of a recorded event. We will take advantage of this in Run 32, where a special detector is included in order to investigate in pulses created by the holding clamps.

ACKNOWLEDGEMENTS

This work was partially supported by funds of the DFG Transregio 27 “Neutrinos and Beyond”, the Munich clus-

ter of Excellence “Origin and Structure of the Universe” and the Maier-Leibnitz-Laboratorium. Support from the Science and Technology Facilities Council (STFC), UK is acknowledged.

REFERENCES

1. P. Meunier, et al., *Appl. Phys. Lett.* **75**, 1335 (1999).
2. G. Angloher et al., *Astroparticle Physics* **31**, 270 (2009).
3. J. C. Lanfranchi, et al., *NIM A* **520**, 135 (2004).
4. M. Kiefer, et al., *Optical Materials* **In Press, Corrected Proof** (2008), arXiv:0809.4975.
5. I. Bavykina, et al., *Optical Materials* **In Press, Corrected Proof** (2008), arXiv:0811.1786.
6. H. Kraus, et al., *Journal of Physics: Conference Series* **39**, 139 (2006).
7. J. Schmaler, et al., “Status of the CRESST Dark Matter Search,” in *Proceedings of the 13th International Workshop on Low-temperature Detectors*, 2009.
8. R. F. Lang, et al., Discrimination of recoil backgrounds in scintillating calorimeters (2009), arxiv:0903.4687.
9. F. Proebst, et al., *J. of Low Temp. Phys.* **100**, 69 (1995).
10. S. Roth, et al., *Optical Materials* **In Press, Corrected Proof** (2008), arXiv:0810.0423v1.